



# Absorption spectra, defect site distribution and upconversion excitation spectra of $\text{CaF}_2/\text{SrF}_2/\text{BaF}_2:\text{Yb}^{3+}:\text{Er}^{3+}$ nanoparticles



Sangeetha Balabhadra <sup>a, b</sup>, Michael F. Reid <sup>a, b</sup>, Vladimir Golovko <sup>a, b</sup>, Jon-Paul R. Wells <sup>a, b, \*</sup>

<sup>a</sup> Dodd-Walls Centre for Photonic and Quantum Technologies, New Zealand

<sup>b</sup> School of Physical and Chemical Sciences, University of Canterbury, PB 4800, Christchurch, 8140, New Zealand

## ARTICLE INFO

### Article history:

Received 28 January 2020

Accepted 11 April 2020

Available online 17 April 2020

### Keywords:

Nanoparticles

Absorption

Cubic site

Cluster centres

Upconversion and excitation dynamics

## ABSTRACT

We report studies of the  $\text{Yb}^{3+}$  site distribution in  $\text{Er}^{3+}$  co-doped upconverting alkaline earth fluoride nanoparticles using high-resolution absorption measurements. It is found that  $\text{Yb}^{3+}$  single ion cubic ( $\text{O}_h$ ) sites and preferentially formed clusters are the dominant centres for moderate dopant concentrations. At higher concentrations, and for larger particle sizes, a minority  $\text{C}_{4v}(\text{F}^-)$  centre is also observed. Furthermore, the behaviour of  $\text{Yb}^{3+}$  cluster centres, whose primary absorption band is centred at  $10205 \text{ cm}^{-1}$  (in near resonance with 980 nm laser diodes) was studied by tuning the metal cation in the host lattice from  $\text{Ca}^{2+} \rightarrow \text{Sr}^{2+} \rightarrow \text{Ba}^{2+}$ . For co-doped materials, with heterogeneous cluster centres,  $\text{Er}^{3+}$  upconversion fluorescence was observed upon selective excitation of  $\text{Yb}^{3+}$ , resulting in a strong visible emission from  $^2\text{H}_{11/2}$ ,  $^4\text{S}_{3/2}$  and  $^4\text{F}_{9/2}$  multiplets. By monitoring the  $\text{Er}^{3+}$  fluorescence, whilst scanning a laser through the wavelength dependent  $\text{Yb}^{3+}$  absorption, we obtain an excitation spectrum for these heterogeneous cluster centres. Spectral features associated with excited state absorption as well as significant deviation from the linear absorption spectra are observed.

© 2020 Elsevier B.V. All rights reserved.

## 1. Introduction

Lanthanide ion ( $\text{Ln}^{3+}$ ) doped upconverting nanoparticles are capable of converting low-energy near-infrared (NIR) photons into high-energy visible photons. This upconversion fluorescence has tremendous importance for a broad spectrum of applications in bio-imaging [1,2], drug delivery [3,4], theranostics [5], photovoltaics [6,7], security [8] and several applications in nanomedicine [9]. In general, upconverting nanomaterials consist of an inert, low-phonon energy, crystalline host matrix (e.g. fluorides) doped with a combination of optically active lanthanide ions ( $\text{Ln}^{3+}$ ). One ion species acts as an energy absorbing sensitizer (typically  $\text{Yb}^{3+}$  or  $\text{Nd}^{3+}$ ) whilst another ion serves as the optically reporting species (e.g.  $\text{Er}^{3+}$ ,  $\text{Tm}^{3+}$ ,  $\text{Ho}^{3+}$ ), which yields fluorescence at the desired wavelength [10]. Amongst the rare earth ions,  $\text{Yb}^{3+}$  has a simple energy level structure with two multiplets ( $^2\text{F}_{5/2}$ ,  $^2\text{F}_{7/2}$ ) and large absorption cross-section near 980 nm, suitable for optical pumping at convenient semiconductor laser diode wavelengths. Despite promising applications in many technologically relevant areas, the

comparatively low upconversion fluorescence yield typically obtained, limits practical application of such materials. Nanoparticles of varying size, dopant concentration, surface modifications, different host, and core/shell nanostructures have been explored to enhance the upconversion fluorescence quantum yield [11]. However, the authors are not aware of investigations which relate these variables to the absorption and excitation spectra. It is crucial to understand the absorption and excitation dynamics of the  $\text{Yb}^{3+}$  ions in upconverting nanoparticles to determine the optimum pump wavelength and to gain insight into the energy transfer processes, which essentially govern the optical properties of lanthanide ion doped nanoparticles.

In the present work,  $\text{Ln}^{3+}$  doped alkaline earth fluorides ( $\text{MF}_2$ ,  $\text{M} = \text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$ ,  $\text{Ba}^{2+}$ ) were chosen as host materials owing to their well-known optical properties such as wide wavelength transparency, low phonon energy ( $495 \text{ cm}^{-1}$  for  $\text{CaF}_2$ ,  $366 \text{ cm}^{-1}$  for  $\text{SrF}_2$ , and  $319 \text{ cm}^{-1}$  for  $\text{BaF}_2$ , respectively) and an extremely large band gap (12 eV) [12–14].  $\text{MF}_2$  crystals have a high-symmetry, cubic structure which is retained even after significant doping. In the cubic centre ( $\text{O}_h$ ) the  $\text{F}^-$  ions form a cage with an  $\text{F}^-$  ion positioned non-locally at each corner in which the single  $\text{Yb}^{3+}$  resides at the centre of each alternate cage. Incorporation of  $\text{Yb}^{3+}$  occurs via the substitution of a cation ( $\text{M}^{2+}$ ) requiring charge compensation via

\* Corresponding author. Dodd-Walls Centre for Photonic and Quantum Technologies, New Zealand.

E-mail address: [jon-paul.wells@canterbury.ac.nz](mailto:jon-paul.wells@canterbury.ac.nz) (J.-P.R. Wells).

negative fluorine ions ( $F^-$ ), positioned locally giving rise to trigonal ( $C_{3v}(F^-)$ ) and tetragonal ( $C_{4v}(F^-)$ )  $Yb^{3+}$  single ion centres [15–17]. However, at higher dopant concentrations preferential clustering of lanthanide ions occurs. It is suggested that these preferential cluster centres scavenge fluoride interstitials and as a result are negatively charged. Such cluster centres appear to have dimer, trimer and even hexameric configurations [18–20]. Numerous techniques such as NMR [21], EXAFS [22], EPR [13,23] and luminescence spectroscopy [12,16,24] have been employed for  $Ln^{3+}$  site-distribution measurements (including the cluster sites), but predominantly for single crystals [25–27] and transparent ceramics [24,28,29]. We are not aware of similarly detailed studies of  $Ln^{3+}$  doped nanoparticles.

We have synthesized water-dispersible, uniform  $Ln^{3+}$  doped  $MF_2$  nanoparticles by a simple hydrothermal method. The nanoparticle phase and structural identification has been performed using powder X-ray diffraction (PXRD) and transmission electron microscopy (TEM) techniques. The absorption spectra of as-synthesized nanoparticles was performed using a high resolution Fourier transform infra-red (FTIR) spectrometer. The nanoparticle site distribution was studied in the 10000–11000  $cm^{-1}$  spectral region and directly compared with bulk crystals of the same nominal concentration. The effect of  $Yb^{3+}$  dopant concentration and nanoparticle size as well as the influence of variation in the ionic radius of the metal cations were systematically investigated. The  $Er^{3+}$  upconversion fluorescence was recorded as a function of excitation wavelength around 980 nm to determine the sub-group of  $Yb^{3+}$  ions, which most efficiently contribute to  $Er^{3+}$  upconversion fluorescence via energy transfer.

## 2. Experimental

### 2.1. Materials

Anhydrous  $CaCl_2$  ( $\geq 95.0\%$ ),  $YbCl_3$  (K&K Laboratories Inc.), anhydrous  $YbF_3$  (Alfa Aesar REacton, 99.9%) and  $CaF_2$  crystal offcuts (Crystran Ltd. UK) were used as starting materials. Ammonium fluoride ( $NH_4F$ , Aldrich 99.99%) and sodium citrate (Fischer Scientific, 99.0%) were used as the fluoride source and stabilizer.  $PbF_2$  (Aldrich, 99 +%) was used as an oxygen scavenger. All the chemicals were used as received without further purification. MilliQ water, and acetone (Analytical grade, 99.98%) were employed in all experiments.

### 2.2. Methods

#### 2.2.1. Synthesis of upconverting nanoparticles

Citrate capped  $CaF_2$  nanoparticles with different  $Yb^{3+}$  molar concentrations (0.1, 1.0, 5.0 and 20.0 mol% in the synthesis medium) were prepared using a hydrothermal method [1]. In detail, stoichiometric quantities of anhydrous  $CaCl_2$ , and  $YbCl_3$  to have nominal molar ratio of  $0.99:0.01-Ca^{2+}:Yb^{3+}$ , with  $3.5 \times 10^{-3}$  mol of the total metal amount, were dissolved in 5 mL of deionized water in a Teflon vessel. A sodium citrate solution (20 mL of a 1.0 M) was added under vigorous stirring for 5 min. Then an ammonium fluoride aqueous solution (2.5 mL of a 3.5 M) was added to the reaction mixture, in order to have a slight excess of fluoride ions,  $(M + Ln^{3+}):F = 1:2.5$  M ratios. The clear solution obtained was heat treated at  $190^\circ C$  for 6 h under autogenous pressure in an autoclave. After that, the autoclave was quickly cooled down to room temperature in order to quench the reaction and to limit further growth (in size) of the nanoparticles. The resulting nanoparticles were obtained by centrifugation. Later washed with milliQ water and acetone, and collected by centrifugation (8000 rpm, 10 min). Nanoparticles are easily dispersible in water to form transparent

colloids. To obtain nanoparticles in powder form, the gel is dried at room temperature for 24 h in air. The samples were denoted according to their molar concentrations of dopants used in the synthesis. Larger nanoparticles were prepared in the same procedure by increasing the reaction time to 48 h and 96 h, respectively. Similarly, the  $Yb^{3+}/Er^{3+}$  co-doped upconverting  $MF_2$  ( $M = Ca^{2+}$ ,  $Sr^{2+}$ ,  $Ba^{2+}$ ) nanoparticles were prepared by using optimal molar concentrations of  $Yb^{3+}/Er^{3+}:20/2$ , in order to avoid concentration quenching and the corresponding non-radiative relaxation processes.

#### 2.2.2. Synthesis of $CaF_2:Yb^{3+}$ bulk crystals

In order to have a direct comparison, bulk  $CaF_2$  crystals were prepared with same  $Yb^{3+}$  nominal concentrations (0.1, 1.0, 5.0 and 20.0 mol%) as nanoparticles. The crystals were grown in graphite crucibles under high vacuum ( $10^{-5}$  Torr), using the vertical Bridgman technique in a 38 kW radio frequency furnace, at temperatures up to  $1500^\circ C$  [2]. The starting material was prepared by crushing up the offcuts of  $CaF_2$  and mixing the appropriate amounts of  $YbF_3$ . A small amount of  $PbF_2$  was added to the charge in order to act as an oxygen scavenger, also resulting in a crystal with reduced concentration of the divalent species. Annealing is achieved via an automatic cooling cycle which leads to improved quality crystals. The as-grown crystals were then cut using a Struers Minitom diamond saw and polished using a Struers LaboPol-2 to give an excellent surface finish for absorption measurements.

### 2.3. Experimental details

#### 2.3.1. Powder X-ray diffraction

Phase identification of the as synthesized powder samples was inferred from their X-ray diffraction patterns. Corresponding diffractograms were collected on a Rigaku SmartLab X-ray diffractometer with  $CuK\alpha_1$  radiation,  $1.5406 \text{ \AA}$ , operating at 40 kV and 30 mA, in the  $2\theta$  range  $20^\circ-90^\circ$  with a  $0.01^\circ$  step size in the reflection scanning mode. The reference data were taken from the International Centre for Diffraction Data (ICDD) database.

#### 2.3.2. Transmission electron microscopy

The morphology of the as synthesized nanoparticle suspensions was analysed on a Philips-CM200 transmission electron microscope (TEM) connected to Gatan Orus CCD camera, operated at 200 kV.

#### 2.3.3. Dynamic light scattering

Dynamic light scattering (DLS) measurements were carried out using a Malvern Zetasizer Nano ZS instrument operating at 532 nm with a 50 mW laser. The data were acquired for sodium citrate capped nanoparticles dispersed to have 0.25 wt% aqueous suspension. The reported values are the average of three measurements.

#### 2.3.4. Fourier-transform infrared spectroscopy (FTIR)

Temperature dependent infrared absorption measurements were performed using Bruker Vertex 80 FTIR having  $0.075 \text{ cm}^{-1}$  resolution with an optical path purged by  $N_2$  gas.

For the absorption measurements, the air-dried powders of nanoparticles were pressed using a pellet maker in order to form a thin pellet ( $\sim 1 \text{ mm}$ ) which was then placed into a small copper sample holder. In the case of crystals, the boule was prepared by first cutting either end with a diamond saw and the ends were polished by different grades of sandpaper. As polished boule was inserted into the copper holder for samples with low  $Yb^{3+}$  concentrations and for the high concentration  $Yb^{3+}$  samples, thin slices ( $\sim 1 \text{ mm}$ ) were cut off of the end of the boule and polished in the

same manner as the boule. The samples were cooled in closed-cycle helium cryostat with temperature variability provided by a resistive heating element.

### 2.3.5. Diode laser emission spectroscopy


Temperature dependent upconversion emission spectra were measured using an Intense 3120 model laser diode controlled with Newport 560B laser diode driver and Newport 350B temperature controller. The laser wavelength is tuned from 975 to 982 nm by changing the laser diode temperature between 283 and 293 K. The free space propagating laser beam was focused on the sample using a LA1608 plano-convex ( $f = 75.0$  mm) aspheric lens (Thorlabs). The laser output power is measured with FieldmaxII laser power meter coupled with the Coherent Powermax (Model PM10) sensor. A range of 0.1–4.0 ND filters (Thorlabs) were used to maintain the laser power at a constant value throughout an experiment. The emission spectra in the visible region was recorded on a modular double grating iHR550 spectrophotometer (Horiba) coupled to a R3896 Hamamatsu photomultiplier. The samples were cooled in Janis closed-cycle helium cryostat with temperature variability provided by a resistive heater controlled by a LakeShore 325 temperature controller. An external UV-VIS mini-spectrometer (Ocean Optics P1000 UV-VIS) was used to monitor the laser diode wavelength.

## 3. Results and discussion

Fig. 1(a) shows the powder X-ray diffraction patterns of  $\text{CaF}_2:\text{Yb}^{3+}$  nanoparticles for varying reaction times from 6 to 96 h

((i)–(iii) at a constant  $\text{Yb}^{3+}$  molar concentration of 1.0 mol%) and for different concentrations of  $\text{Yb}^{3+}$  in the synthesis media between 0.1 and 20.0 mol% ((iv)–(vi) using a constant reaction time of 6 h). The samples exhibit the cubic phase of  $\text{CaF}_2$  (space group  $Fm\bar{3}m$ ), in agreement with ICDD card (04–002–4443) and as reported by Pedroni et al. [30]. No new diffraction peaks are observed when the amount of  $\text{Yb}^{3+}$  increases from 0.1 to 20.0 mol% nor as the reaction time increases, indicating that these ions have been effectively introduced into the  $\text{CaF}_2$  lattice. The diffraction peaks of the nanoparticles in Fig. 1(a) ((iii) and (vi)) show a slight shift towards lower angles, in comparison to the other nanoparticles which can be due to the sample displacement.

Fig. 1(b) displays the powder X-ray diffraction patterns of  $\text{MF}_2:20.0$  mol%  $\text{Yb}^{3+}:2.0$  mol%  $\text{Er}^{3+}$  nanoparticles where  $M = \text{Ba}^{2+}$ ,  $\text{Sr}^{2+}$ , and  $\text{Ca}^{2+}$  ((i)–(iii)), respectively. The samples are of pure cubic crystalline phase (space group  $Fm\bar{3}m$ ), in agreement with ICDD cards 00–004–0452 for  $\text{BaF}_2$ , 04–016–6744 for  $\text{SrF}_2$ , and 04–002–4443 for  $\text{CaF}_2$ , respectively. From the diffractograms the average size of the crystallite domains in nanoparticles could be estimated using Scherrer's equation (Table S1 in supporting information) using the full-width half-maximum value of the  $2\theta$  diffraction peak at  $46.9^\circ$  (i.e. the (220) plane). In addition, the hydrodynamic size distribution of the nanoparticles was also measured using dynamic light scattering (DLS, see Fig. S1 and Table S1 in the supporting information). The hydrodynamic sizes are in good agreement with the average crystallite sizes calculated from the PXRD results. Representative transmission electron microscopy (TEM) images of the  $\text{CaF}_2:5.0$  mol%  $\text{Yb}^{3+}$  nanoparticles are shown in Fig. 1(c) which illustrates that the nanoparticles are spherical and homogeneously

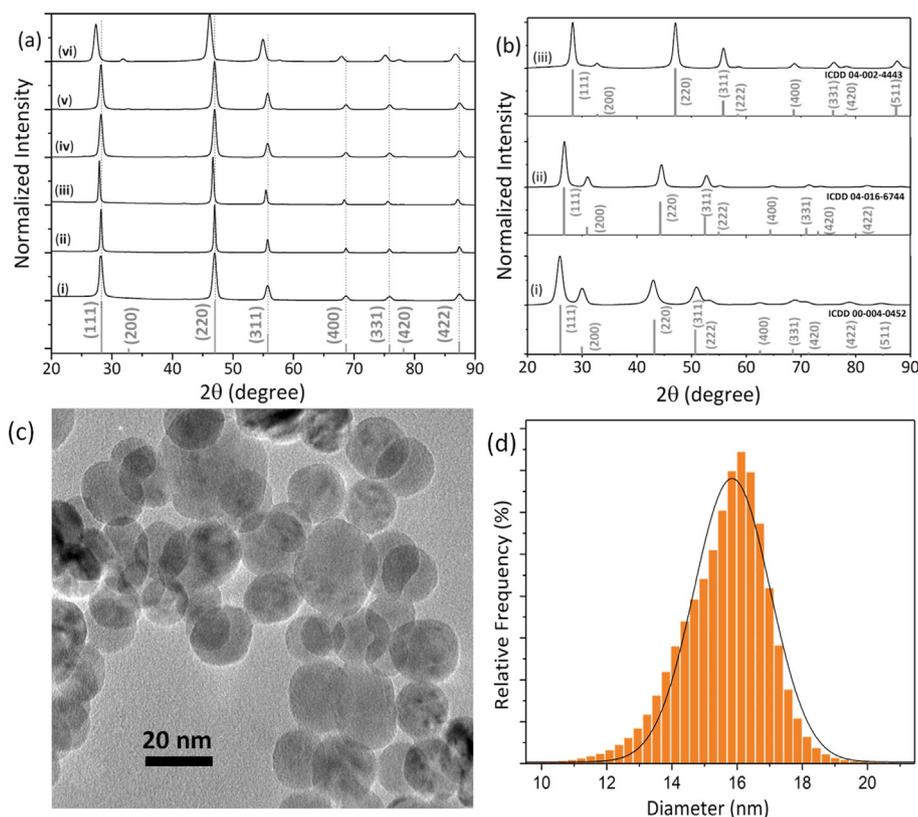

**Fig. 1.** Powder X-ray diffraction patterns of (a)  $\text{CaF}_2$  nanoparticles prepared at reaction times (i) 6 h, (ii) 48 h and (iii) 96 h for 1 mol% of  $\text{Yb}^{3+}$  molar concentrations; doped with (iv) 0.1 mol%, (v) 5.0 mol%, and (vi) 20.0 mol% of  $\text{Yb}^{3+}$  concentrations at reaction time of 6 h. (b)  $\text{MF}_2:20.0$  mol%  $\text{Yb}^{3+}:2.0$  mol%  $\text{Er}^{3+}$  nanoparticles where (i)  $M = \text{Ba}^{2+}$ , (ii)  $M = \text{Sr}^{2+}$ , and (iii)  $M = \text{Ca}^{2+}$ . The diffraction patterns of cubic  $\text{BaF}_2$  (ICDD Card No 00–004–0452),  $\text{SrF}_2$  (ICDD Card No 04–016–6744), and  $\text{CaF}_2$  (ICDD Card No 04–002–4443), are also depicted. (c) Transmission electron microscope image and (d) corresponding size distribution histogram of  $\text{CaF}_2:5.0$  mol%  $\text{Yb}^{3+}$  nanoparticles. A total of 100 nanoparticles were measured. The solid line is the best fit of the experimental data to a Gaussian distribution ( $r^2 > 0.989$ ).

distributed. As shown in the size distribution histogram in Fig. 1(d), the diameter of the nanoparticles ranges from 8 to 22 nm, with average values of  $15.8 \pm 2.1$  nm. The TEM nanoparticle size distribution is in good agreement with the hydrodynamic sizes from DLS and the average crystallite sizes calculated from the PXRD results.

Fig. 2(a) and (b) shows the FTIR absorption spectra measured for nanoparticles and bulk crystals as a function of  $\text{Yb}^{3+}$  ion molar concentration, recorded for samples cooled to 10 K (at 25 K for the  $\text{CaF}_2:0.1$  mol%  $\text{Yb}^{3+}$  crystal). All samples display characteristic absorption features associated with the  ${}^2F_{7/2} \rightarrow {}^2F_{5/2}$   $\text{Yb}^{3+}$  intermultiplet transition in the  $10100\text{--}11000\text{ cm}^{-1}$  spectral region. These absorption spectra have been extensively studied for bulk crystals, and the literature data [12,16,17,31] is in excellent agreement with our observations for high quality, oxygen free samples. The  $\text{CaF}_2:0.1$  mol%  $\text{Yb}^{3+}$  crystal (Fig. 2(b) (i)) has very sharp lines, corresponding to the single ion centres: cubic ( $\text{O}_h$ :10381 and  $10840\text{ cm}^{-1}$ ), tetragonal ( $\text{C}_{4v}(\text{F}^-)$ :10321, 10401 and  $11000\text{ cm}^{-1}$ ), trigonal ( $\text{C}_{3v}(\text{F}^-)$ :10257, 10375, and  $10712\text{ cm}^{-1}$ ) as well as lines assigned to  $\text{Yb}^{3+}$  clusters (10199, and  $10205\text{ cm}^{-1}$ ). In crystals with high  $\text{Yb}^{3+}$  concentrations (Fig. 2(b) ((ii)–(iv))) the absorption spectra are completely dominated by cubic and clusters centres. It can be speculated that as the population of negatively charged cluster centres increases, there is an associated rise in the population of non-locally charge compensated cubic centres.

For nanoparticles doped with 0.1 mol%  $\text{Yb}^{3+}$  the absorption spectra consist of isolated cubic centres (corresponding to the feature at  $10381\text{ cm}^{-1}$ ). The feature denoted by an \* appears to be associated with perturbed cubic centres, possibly residing near the nanoparticle surface. We note that the bulk crystal are synthesized by the Bridgman-Stockbarger technique ( $1500\text{ }^\circ\text{C}$ ) and the nanoparticles by a hydrothermal method ( $190\text{ }^\circ\text{C}$ ) [32–34]. High-temperature crystal growth gives scope for the ions to freely move and to arrange themselves in a minimum energy configuration [35]. This favours the formation of lower symmetry sites such as the  $\text{C}_{3v}(\text{F}^-)$  and  $\text{C}_{4v}(\text{F}^-)$  centres. At higher  $\text{Yb}^{3+}$  concentrations, the spectra indicate that the nanoparticle site distribution resembles more closely that observed for the bulk crystals - being dominated by cluster and cubic sites. However, there are clearly differences in detail. Both in bulk crystals and nanoparticles, the feature centred around  $10850\text{ cm}^{-1}$  contains contributions from both the cubic and cluster centres. With an increase in  $\text{Yb}^{3+}$  concentration there is a noticeable increase of this feature along with the cluster centre absorption feature at  $10205\text{ cm}^{-1}$ . The absorption spectra recorded at room temperature for both bulk crystals and nanoparticles (Fig. S2 in supporting information) clearly shows

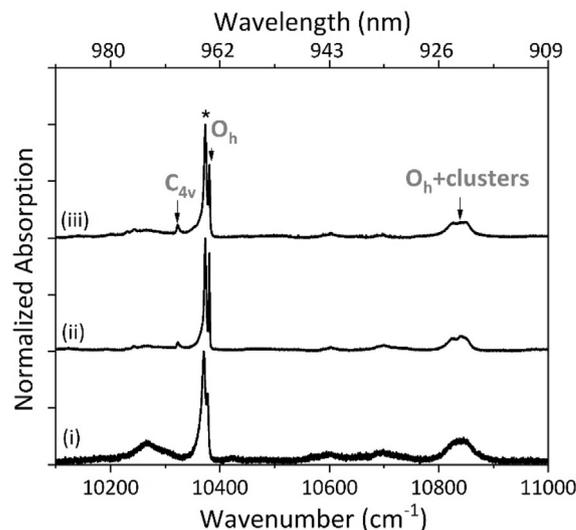


Fig. 3. FTIR absorption spectra measured at 10 K for  $\text{CaF}_2:1.0$  mol%  $\text{Yb}^{3+}$  nanoparticles at reaction times of (i) 6 h, (ii) 48 h and (iii) 96 h, respectively. The feature marked \* appears to be perturbed cubic centres.

both the cubic and cluster centres, although the transitions are broadened in comparison with 10 K.

To understand the influence of nanoparticle size on the observed site distribution, different reaction times between 6, 48 and 96 h were used, resulting in particle diameters increasing from 12.1 nm, to 35.4 nm and to 52.6 nm, increasing the reaction time. The average diameters of the nanoparticles measured using TEM correlate nicely with crystallite sizes based on PXRD and hydrodynamic sizes based on DLS measurements (Fig. 1, Fig. S1 and Table S1 in supporting information). In the larger nanoparticles, the absorption spectra also have weak absorption features from tetragonal  $\text{C}_{4v}(\text{F}^-)$  sites (see Fig. 3).

Upconverting nanoparticles containing  $\text{Yb}^{3+}$  as the energy absorbing ion, are commonly pumped by strained layer, multi-quantum well InGaAs laser diodes having an output wavelength near 980 nm ( $10205\text{ cm}^{-1}$ ). The typical dopant concentrations used lie in the 16.0–20.0 mol% range due to the requirement for high absorption depth (see Fig. 2(a) (iv)) [36]. It would be standard for the reporting ion (e.g.  $\text{Er}^{3+}$ ) to be doped in the 1.0–2.0 mol% range.

Fig. 4(i)–(iii) shows the 10 K FTIR absorption spectra for


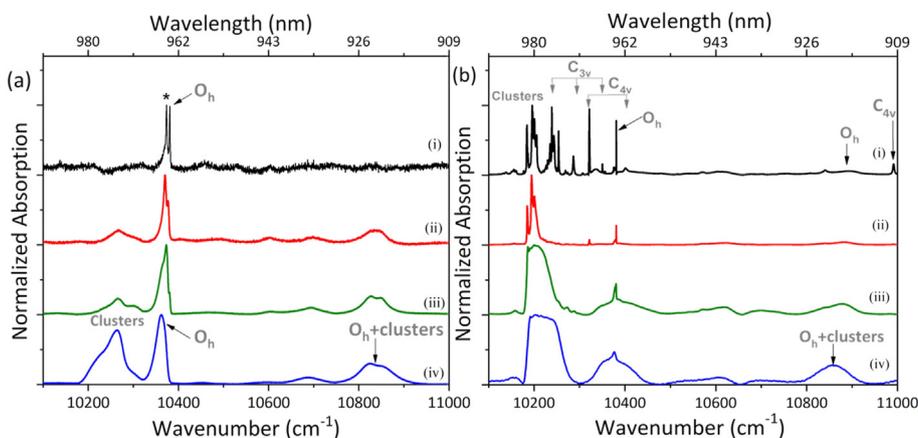


Fig. 2. FTIR absorption spectra measured at 10 K for  $\text{CaF}_2$  doped with (i) 0.1, (ii) 1.0, (iii) 5.0 and (iv) 20.0 mol%  $\text{Yb}^{3+}$  concentrations for (a) nanoparticles and (b) crystals. The spectrum for the  $\text{CaF}_2:0.1$  mol%  $\text{Yb}^{3+}$  crystal was recorded at 25 K. The feature marked \* appears to be perturbed cubic centres.

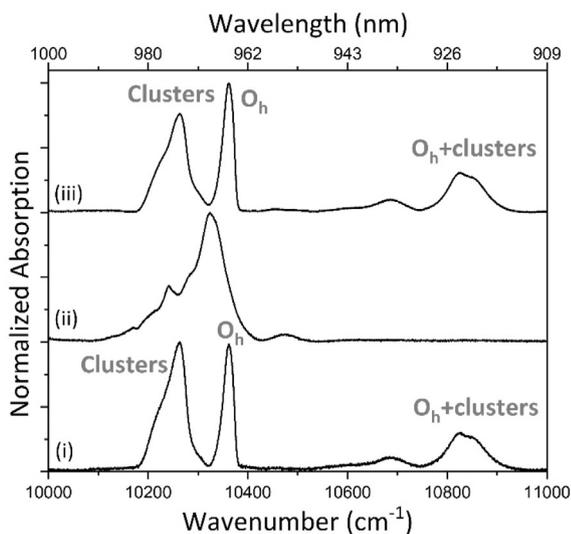


**Fig. 4.** FTIR absorption spectra measured at 10 K for CaF<sub>2</sub> nanoparticles doped with (i) 20.0 mol% Yb<sup>3+</sup>, (ii) 20.0 mol% Er<sup>3+</sup> and (iii) 20.0 mol% Yb<sup>3+</sup>/2.0 mol% Er<sup>3+</sup>.

20.0 mol% Yb<sup>3+</sup>: 20.0 mol% Er<sup>3+</sup> and 20.0 mol% Yb<sup>3+</sup>:2.0 mol% Er<sup>3+</sup> co-doped upconverting nanoparticles. The absorption spectrum of 20.0 mol% Yb<sup>3+</sup> doped CaF<sub>2</sub> nanoparticles shown in Fig. 4(i) has features attributable to cubic as well as cluster centres. When doped with Er<sup>3+</sup>, the prominent characteristics of the Yb<sup>3+</sup> single ion sites remain essentially intact. Trivalent erbium has a broad absorption band which resides near 10340 cm<sup>-1</sup> corresponding to the <sup>4</sup>I<sub>15/2</sub> → <sup>4</sup>I<sub>11/2</sub> transition [37], whose absorption tail closely overlaps with the Yb<sup>3+</sup> cluster centre absorption. The absorption cross-section of Yb<sup>3+</sup> ions in the 10100–11000 cm<sup>-1</sup> region is much


larger than that for the Er<sup>3+</sup> ions (Fig. 4) thus the energy transfer from Yb<sup>3+</sup> to Er<sup>3+</sup> via the channel <sup>2</sup>F<sub>5/2</sub>(Yb<sup>3+</sup>)+<sup>4</sup>I<sub>15/2</sub>(Er<sup>3+</sup>)→<sup>2</sup>F<sub>7/2</sub>(Yb<sup>3+</sup>)+<sup>4</sup>I<sub>11/2</sub>(Er<sup>3+</sup>) efficiently sensitizes the luminescence of Er<sup>3+</sup> [38].

It becomes immediately clear that an excitation source fixed at 980 nm (having a typical linewidth of approximately 3 nm, e.g. an Intense model 3120 laser diode) is not optimally resonant with the absorption features of the Yb<sup>3+</sup> clusters in CaF<sub>2</sub> based nanoparticles. Varying the cation may yield a shift in the resonance peak thus improving the coupling efficiency. We have measured the absorption spectra of Yb<sup>3+</sup>:Er<sup>3+</sup> co-doped MF<sub>2</sub> (M = Ba<sup>2+</sup>, Sr<sup>2+</sup>, and Ca<sup>2+</sup>) nanoparticles which are shown in Fig. 5(a). Changing the cation in the sequence from Ca<sup>2+</sup>→Sr<sup>2+</sup>→Ba<sup>2+</sup> results in a very significant broadening of the absorption transitions which is highly favorable as an energy conduit which is stable against minor wavelength fluctuations in the pump laser system. It also suggests broadband excitation via LEDs might be a viable option.

Fig. 5(b) shows the upconversion fluorescence spectra, excited using a 980 nm laser diode employing a power density of 31 Wcm<sup>-2</sup> at the sample. Application relevant room temperature fluorescence spectra are presented here (the 10 K data (Fig. S5) can be found in the supporting information). All three upconverting nanoparticle samples exhibit upconversion fluorescence which can be assigned to the <sup>2</sup>H<sub>11/2</sub> → <sup>4</sup>I<sub>15/2</sub> (520 nm), <sup>4</sup>S<sub>3/2</sub> → <sup>4</sup>I<sub>15/2</sub> (540 nm) and <sup>4</sup>F<sub>9/2</sub> → <sup>4</sup>I<sub>15/2</sub> (650 nm) transitions of Er<sup>3+</sup>. The upconverting nanoparticle fluorescence follows same trend at cryogenic temperatures (Fig. S5). However by tuning the laser to 975 nm, the absorption is significantly higher for all three samples (when compared for nanoparticles with similar dopant concentration) and we observe an increase in the upconversion fluorescence intensities as shown in Fig. 5(c). Overall, it is evident that SrF<sub>2</sub> upconverting nanoparticles exhibit the most intense upconversion fluorescence, which we speculate is due to the low phonon-energy (366 cm<sup>-1</sup>) and a strong absorption band in the 980-970 nm region.

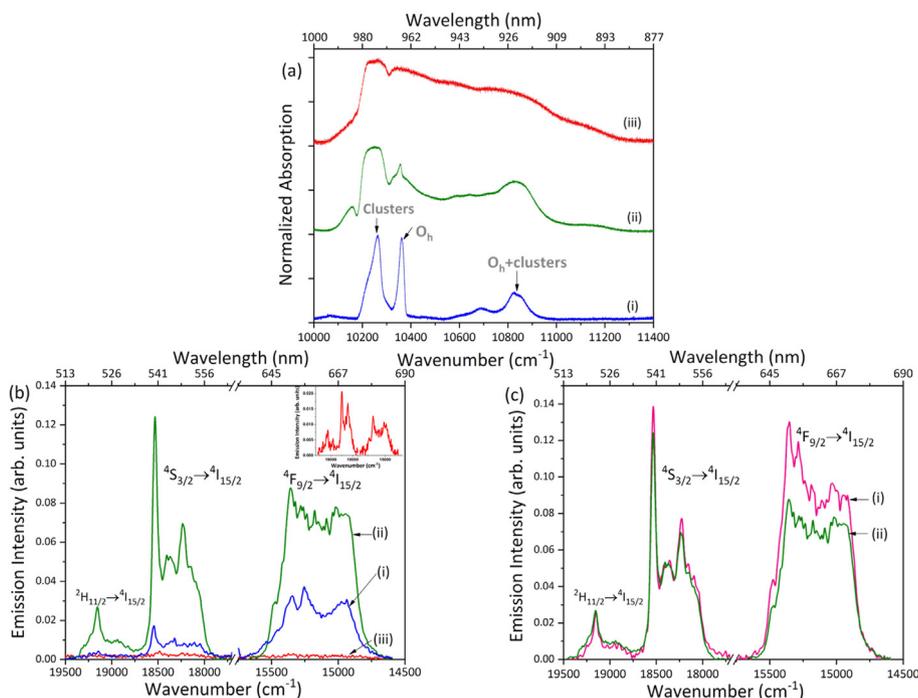

**Fig. 5.** (a) FTIR absorption spectra measured at 10 K and (b) room temperature upconversion fluorescence spectra measured for MF<sub>2</sub>:20.0 mol%Yb<sup>3+</sup>/2.0 mol% Er<sup>3+</sup> nanoparticles where M = (i) Ca<sup>2+</sup> (ii) Sr<sup>2+</sup> and (iii) Ba<sup>2+</sup> nanoparticles at 980 nm laser excitation and (c) SrF<sub>2</sub>:20.0 mol%Yb<sup>3+</sup>/2.0 mol% Er<sup>3+</sup> nanoparticles exciting at laser wavelength of (i) 975 nm and (ii) 980 nm. Inset in (b) is the zoom in of upconversion fluorescence spectrum of BaF<sub>2</sub>:20.0 mol%Yb<sup>3+</sup>/2.0 mol% Er<sup>3+</sup> nanoparticles on an expanded scale. A laser power density of 31 W cm<sup>-2</sup> was used to record the upconversion fluorescence spectra.

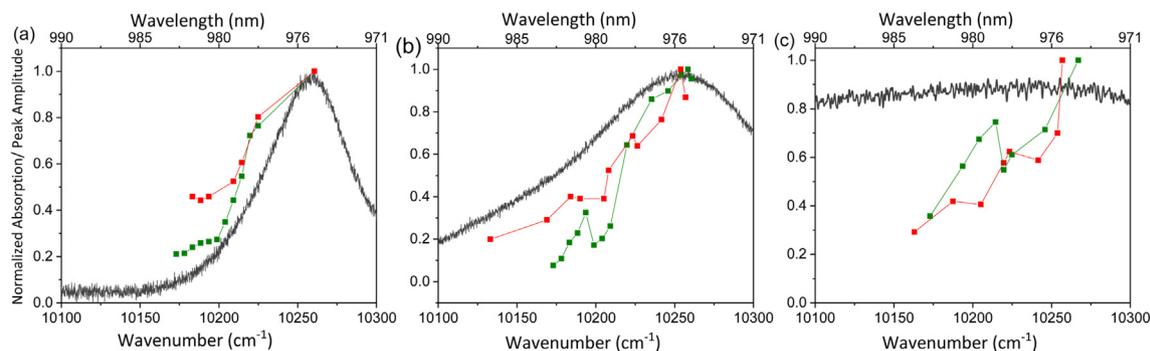

**Fig. 6.**  $\text{Yb}^{3+}$  excitation profile measured monitoring  $\text{Er}^{3+}$  ion  $4\text{S}_{3/2} \rightarrow 4\text{I}_{15/2}$  (540 nm) peak amplitude for  $\text{MF}_2:20.0 \text{ mol}\% \text{Yb}^{3+}/2.0 \text{ mol}\% \text{Er}^{3+}$  nanoparticles where  $M =$  (a)  $\text{Ca}^{2+}$  (b)  $\text{Sr}^{2+}$  and (c)  $\text{Ba}^{2+}$  nanoparticles at room temperature, respectively. The excitation profiles were measured for the  $\text{Er}^{3+} 4\text{S}_{3/2} \rightarrow 4\text{I}_{15/2}$  (540 nm, green dotted lines) and  $4\text{F}_{9/2} \rightarrow 4\text{I}_{15/2}$  (650 nm, red dotted lines) transitions. All data have been normalized to the maximum data point. (For interpretation of the references to colour in this figure legend, the reader is referred to the Web version of this article.)

We note that although  $\text{BaF}_2$  has a lower phonon energy ( $319 \text{ cm}^{-1}$ ) it has very weak emission (Fig. 5(b) inset) due to its spectrally broad and low peak amplitude absorption spectra – these may be more suitably pumped with a broadband light source. Moreover,  $\text{BaF}_2$  nanocrystals tend to have a distorted crystal structure when high concentrations of low ionic radius  $\text{Yb}^{3+}$  (0.086 nm) and  $\text{Er}^{3+}$  (0.089 nm) replace the high ionic radius  $\text{Ba}^{2+}$  (0.135 nm). In  $\text{CaF}_2$  nanoparticles, the upconversion fluorescence yields predominantly red emission ( $4\text{F}_{9/2} \rightarrow 4\text{I}_{15/2}$ ) when compared to the observed spectra for the  $\text{SrF}_2$  and  $\text{BaF}_2$  nanoparticles. This is presumably a result of the high-phonon energy ( $495 \text{ cm}^{-1}$ ) giving a higher probability of non-radiative relaxation to the lower energy emitting state in the  $\text{CaF}_2$  host lattice [38].

Fig. 6 shows the excitation spectra obtained monitoring the  $\text{Er}^{3+}$  fluorescence  $4\text{S}_{3/2} \rightarrow 4\text{I}_{15/2}$  (540 nm, green dotted lines) and  $4\text{F}_{9/2} \rightarrow 4\text{I}_{15/2}$  (650 nm, red dotted lines) transitions, while scanning the laser sequentially across the  $\text{Yb}^{3+}$  absorption profile, measured for all three bare nanoparticle materials and compared against their corresponding absorption spectra (solid lines in Fig. 6). These excitation and absorption spectra were measured at room temperature. The excitation profile was recorded at low laser power densities  $4 \text{ W cm}^{-2}$  ( $\text{SrF}_2$  and  $\text{CaF}_2$ ) and  $14 \text{ W cm}^{-2}$  ( $\text{BaF}_2$ ) where UC fluorescence has a linear dependence with a slope of approximately two when plotted on a log-log plot. Cryogenically cooling the samples yields no appreciable difference. Within the wavelength range of the diode used, all three materials exhibit the highest emission yield near  $10250 \text{ cm}^{-1}$  (975 nm) which is also where the nanoparticles have the maximum absorption. However, the spectral dependence of the upconversion fluorescence does not, in all cases, reflect the absorption spectra. The observed deviation becomes successively more pronounced as the ionic radius of the metal cation increases. For  $\text{BaF}_2$  nanoparticles the upconversion fluorescence amplitude decreases to 30% of its peak value at  $10150 \text{ cm}^{-1}$ , however the absorption depth at this frequency is unchanged. It is also observable that a comparatively sharp peak is present at  $10194$  and  $10215 \text{ cm}^{-1}$  for  $\text{SrF}_2$  and  $\text{BaF}_2$  respectively. Again, this is not reflected in the absorption spectra and appears to be an excited state absorption feature. Of course, upconversion is a complex, nonlinear, process, but we may tentatively interpret the lack of simple proportionality as indicating that only a subset of the absorbing  $\text{Yb}^{3+}$  ions are located in heterogeneous clusters contained the emitting ion,  $\text{Er}^{3+}$ , with the remaining ions residing in clusters containing only  $\text{Yb}^{3+}$  ions (Fig. 6). Thus the Yb absorption profile cannot be used as an indicator of the optimum excitation wavelength and measurement of both the absorption and upconversion excitation spectra of upconverting nanomaterials

(especially the most commonly used nanoparticles e.g.  $\text{NaYF}_4$ ) is required, in order to increase the upconversion fluorescence yield, which is the bottleneck holding back practical implementation of the existing nanoparticle materials.

#### 4. Conclusions

In summary, cubic phase single ion doped ( $\text{Yb}^{3+}$ ) and multi-ion doped ( $\text{Yb}^{3+}/\text{Er}^{3+}$ )  $\text{MF}_2$  ( $M = \text{Ca}^{2+}$ ,  $\text{Sr}^{2+}$ , and  $\text{Ba}^{2+}$ ) nanoparticles have been successfully synthesized by a simple hydrothermal route at moderate temperatures and ambient pressure. Their structure and morphology were characterized by the PXRD, TEM, and DLS techniques. The absorption spectra of the as synthesized nanoparticles were investigated using FTIR spectroscopy and directly compared with data for the bulk single crystals of the same dopant concentrations. The  $\text{Yb}^{3+}$  ion site distribution is dominated by both non-locally charge compensated cubic centres and preferentially formed multi-ion cluster centres. Measurements of the spectral dependence of the  $\text{Er}^{3+}$  upconversion fluorescence obtained whilst pumping  $\text{Yb}^{3+}$  exhibit increasingly large deviations from the linear absorption spectrum as the size of the metal cation increases. In addition, excited state absorption features can be observed. The former appears to indicate an increase in homogeneous Yb–Yb clustering however the absorption maximum is still observed to coincide with the maximum in the  $\text{Er}^{3+}$  upconversion fluorescence.

#### Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

#### CRediT authorship contribution statement

**Sangeetha Balabhadra:** Conceptualization, Investigation, Methodology, Formal analysis, Writing - original draft, Writing - review & editing. **Michael F. Reid:** Conceptualization, Investigation, Methodology, Formal analysis, Writing - review & editing, Supervision. **Vladimir Golovko:** Investigation, Writing - review & editing. **Jon-Paul R. Wells:** Conceptualization, Investigation, Methodology, Formal analysis, Writing - review & editing, Project administration, Supervision.

#### Acknowledgements

The authors acknowledge the expert technical assistance of Dr

Mathew Polson, Mr Shaun Mucalo, Mr Stephen Hemmingsen, Mr Robert Thirkettle and Mr Nick Olivier.

## Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.jallcom.2020.155165>.

## References

- [1] M. Bettinelli, L.D. Carlos, X. Liu, Lanthanide-doped upconversion nanoparticles, *Phys. Today* 68 (2015) 38–44.
- [2] E. Hemmer, N. Venkatachalam, H. Hyodo, A. Hattori, Y. Ebina, H. Kishimoto, K. Soga, Upconverting and NIR emitting rare earth based nanostructures for NIR-bioimaging, *Nanoscale* 5 (2013) 11339–11361.
- [3] Y.M. Yang, Upconversion nanophosphors for use in bioimaging, therapy, drug delivery and bioassays, *Microchim. Acta.* 181 (2014) 263–294.
- [4] J.-C.G. Bünzli, Lanthanide luminescence for biomedical analyses and imaging, *Chem. Rev.* 110 (2010) 2729–2755.
- [5] H. Qiu, M. Tan, T.Y. Ohulchansky, J.F. Lovell, G. Chen, Recent progress in upconversion photodynamic therapy, *Nanomaterials* 8 (2018) 1–18.
- [6] J. de Wild, A. Meijerink, J.K. Rath, W.G.J.H.M. van Sark, R.E.I. Schropp, Upconverter solar cells: materials and applications, *Energy Environ. Sci.* 4 (2011) 4835–4848.
- [7] H.-Q. Wang, M. Batentschuk, A. Osvet, L. Pinna, C.J. Brabec, Rare-earth ion doped up-conversion materials for photovoltaic applications, *Adv. Mater.* 23 (2011) 2675–2680.
- [8] W. Cross, T. Blumenthal, J. Kellar, P.S. May, J. Meruga, Q. Luu, Rare-earth doped nanoparticles in security printing applications, *MRS Proceedings* 1471 (2012) 62–67.
- [9] B. Zhou, B. Shi, D. Jin, X. Liu, Controlling upconversion nanocrystals for emerging applications, *Nat. Nanotechnol.* 10 (2015) 924–936.
- [10] G. Chen, H. Qiu, P.N. Prasad, X. Chen, Upconversion nanoparticles: design, nanochemistry, and applications in theranostics, *Chem. Rev.* 114 (2014) 5161–5214.
- [11] M. Haase, H. Schaefer, Upconverting nanoparticles, *Angew. Chemie-International Edition* 50 (2011) 5808–5829.
- [12] B. Lacroix, C. Genevois, J.L. Doualan, G. Brasse, A. Braud, P. Ruterana, P. Camy, E. Talbot, R. Moncorgé, J. Margerie, Direct imaging of rare-earth ion clusters in Yb:CaF<sub>2</sub>, *Phys. Rev. B Condens. Matter* 90 (2014), 125124-14.
- [13] M.L. Falin, K.I. Gerasimov, V.A. Latypov, A.M. Leushin, EPR and optical spectroscopy of Yb<sup>3+</sup> ions in CaF<sub>2</sub>: an analysis of the structure of tetragonal centers, *Appl. Magn. Reson.* 26 (2004) 617–632.
- [14] M. Siebold, S. Bock, U. Schramm, B. Xu, J.L. Doualan, P. Camy, R. Moncorgé, Yb:CaF<sub>2</sub>—a new old laser crystal, *Appl. Phys. B* 97 (2009) 327–338.
- [15] J.M. Baker, E.R. Davies, J.P. Hurrell, Electron nuclear double resonance in calcium fluoride containing Yb<sup>3+</sup> and Ce<sup>3+</sup> in tetragonal sites, *P. Roy.Soc.Lond. A. Mat.* 308 (1969) 403–431.
- [16] V. Petit, P. Camy, J.L. Doualan, X. Portier, R. Moncorgé, Spectroscopy of Yb<sup>3+</sup>:CaF<sub>2</sub>: from isolated centers to clusters, *Phys. Rev. B-Condensed Matter and Materials Physics* 78 (2008), 085131-12.
- [17] S.A. Kazanskii, A.I. Ryskin, Clusters of group-III ions in activated fluorite-type crystals, *Phys. Solid State* 44 (2002) 1415–1425.
- [18] K.M. Cirillo-Penn, J.C. Wright, Identification of defect structures in Eu<sup>3+</sup>:CaF<sub>2</sub> by site selective spectroscopy of relaxation dynamics, *J. Lumin.* 48–49 (1991) 505–508.
- [19] M.B. Seelbinder, J.C. Wright, Site-selective spectroscopy of CaF<sub>2</sub>:Ho<sup>3+</sup>, *Phys. Rev. B* 20 (1979) 4308–4320.
- [20] J. Kirton, S.D. McLaughlan, Correlation of electron paramagnetic resonance and optical-absorption spectra of CaF<sub>2</sub>:Yb<sup>3+</sup>, *Phys. Rev.* 155 (1967) 279–284.
- [21] R.J. Booth, B.R. McGarvey, <sup>19</sup>F NMR studies of CaF<sub>2</sub> crystals doped with NdF<sub>3</sub>, EuF<sub>3</sub>, DyF<sub>3</sub>, HoF<sub>3</sub> or TmF<sub>3</sub>, *Phys. Rev. B* 21 (1980) 1627–1635.
- [22] C.R.A. Catlow, A.V. Chadwick, G.N. Greaves, L.M. Moroney, Direct observations of the dopant environment in fluorites using EXAFS, *Nature* 312 (1984) 601–604.
- [23] M.L. Falin, K.I. Gerasimov, V.A. Latypov, A.M. Leushin, H. Bill, D. Lovy, EPR and optical spectroscopy of Yb<sup>3+</sup> ions in CaF<sub>2</sub> and SrF<sub>2</sub>, *J. Lumin.* 102–103 (2003) 239–242.
- [24] T. Kallel, M.A. Hassairi, M. Dammak, A. Lyberis, P. Gredin, M. Mortier, Spectra and energy levels of Yb<sup>3+</sup> ions in CaF<sub>2</sub> transparent ceramics, *J. Alloys Compd.* 584 (2014) 261–268.
- [25] S.M. Kaczmarek, T. Tsuboi, M. Ito, G. Boulon, G. Leniec, Optical study of Yb<sup>3+</sup>/Yb<sup>2+</sup> conversion in CaF<sub>2</sub> crystals, *J. Phys. Condens. Matter* 17 (2005) 3771–3786.
- [26] A.S. Shcheulin, A.E. Angervaks, T.S. Semenova, L.F. Koryakina, M.A. Petrova, P.P. Fedorov, V.M. Reiterov, E.A. Garibin, A.I. Ryskin, Additive colouring of CaF<sub>2</sub>:Yb crystals: determination of Yb<sup>2+</sup> concentration in CaF<sub>2</sub>:Yb crystals and ceramics, *Appl. Phys. B* 111 (2013) 551–557.
- [27] M. Stef, A. Pruna, N. Pecingina-Garjoaba, I. Nicoara, Influence of various impurities on the optical properties of YbF<sub>3</sub>-doped CaF<sub>2</sub> crystals, *Acta Phys. Pol., A* 112 (2007) 1007–1012.
- [28] R.J. Hamers, J.R. Wietfeldt, J.C. Wright, Defect chemistry in CaF<sub>2</sub>:Eu<sup>3+</sup>, *J. Chem. Phys.* 77 (1982) 683–692.
- [29] P.P. Fedorov, Chapter 4 - fluoride laser ceramics, in: B. Denker, E. Shklovsky (Eds.), *Handbook of Solid-State Lasers*, Woodhead Publishing, 2013, pp. 82–109.
- [30] M. Pedroni, F. Piccinelli, T. Passuello, S. Polizzi, J. Ueda, P. Haro-Gonzalez, L. Martinez Maestro, D. Jaque, J. García-Sole, M. Bettinelli, A. Speghini, Water (H<sub>2</sub>O and D<sub>2</sub>O) dispersible NIR-to-NIR upconverting Yb<sup>3+</sup>/Tm<sup>3+</sup> doped MF<sub>2</sub> (M = Ca, Sr) colloids: influence of the host crystal, *Cryst. Growth Des.* 13 (2013) 4906–4913.
- [31] K. Yu, V.V.O. Voronko, I.A. Shcherbakov, Optical centers and the interactions of Yb<sup>3+</sup> ions in cubic fluorite crystals, *Sov. Phys. - JETP* 29 (1969) 86–90.
- [32] M. Wang, G. Abbineni, A. Clevenger, C. Mao, S.H. Xu, Upconversion nanoparticles: synthesis, surface modification and biological applications, *Nanomed. Nanotechnol. Biol. Med.* 7 (2011) 710–729.
- [33] S.H. Feng, G.H. Li, R. Xu, Chapter 4 - hydrothermal and solvothermal syntheses, in: Y. Xu (Ed.), *Modern Inorganic Synthetic Chemistry*, second ed., Elsevier, Amsterdam, 2017, pp. 73–104.
- [34] K. Byrappa, T. Adschiri, Hydrothermal technology for nanotechnology, *Prog. Cryst. Growth Char. Mater.* 53 (2007) 117–166.
- [35] I. Elswie, Z. Lazarevic, V. Radojevic, M. Gilic, M. Rabasovic, D. Sevic, N. Romcevic, The bridgman method growth and spectroscopic characterization of calcium fluoride single crystals, *Sci. Sinter.* 48 (2016) 333–341.
- [36] F. Vetrone, J.-C. Boyer, J.-A. Capobianco, Significance of Yb<sup>3+</sup> concentration on the upconversion mechanisms in codoped Y<sub>2</sub>O<sub>3</sub>:Er<sup>3+</sup>, Yb<sup>3+</sup> nanocrystals, *J. Appl. Phys.* 96 (2004) 661–667.
- [37] W. Ma, L. Su, X. Xu, J. Wang, D. Jiang, L. Zheng, X. Fan, C. Li, J. Liu, J. Xu, Effect of erbium concentration on spectroscopic properties and 2.79 μm laser performance of Er:CaF<sub>2</sub> crystals, *Opt. Mater. Express* 6 (2016) 409–415.
- [38] M.Y. Hossan, A. Hor, Q. Luu, S.J. Smith, P.S. May, M.T. Berry, Explaining the nanoscale effect in the upconversion dynamics of β-NaYF<sub>4</sub>:Yb<sup>3+</sup>, Er<sup>3+</sup> core and core-shell nanocrystals, *J. Phys. Chem. C* 121 (2017) 16592–16606.